


CRYSTACAL R

Fibrous and Decorative Plaster

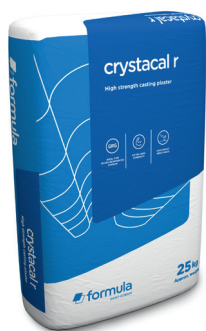

PRODUCT DESCRIPTION

Crystacal R is a formulated hemihydrate plaster ($\text{CaSO}_4 \cdot \frac{1}{2}\text{H}_2\text{O}$) produced from naturally occurring high purity gypsum mineral. It is white in colour.

This product is used to make hard casts with fine reproduction of detail. It is used in the manufacture of glass reinforced gypsum structures, decorative plasterwork and giftware.

PRODUCT BENEFITS

- + Produces hard casts with good reproduction of fine detail
- + Shelf life of 9 months

APPLICATION

Fibrous & GRG

TECHNICAL INFORMATION

Chemical name	Calcium sulphate hemihydrate
Chemical composition	$\text{CaSO}_4 \cdot \frac{1}{2}\text{H}_2\text{O}$
Plaster to water ratio (by weight)	2.86:1
Water to plaster ratio (by weight)	35%
Plaster to water mix ratio (by weight)	100/35
Colour	White
Colorometer L* value	92.5
Colorometer a* value	0.5
Colorometer b* value	3.5
Initial setting time (minutes)	15
Final setting time (minutes)	18
Linear Expansion (%)	0.4
Flexural strength (MPa)	11
Brinell hardness (MPa)	190
Dry compressive strength (Mpa)	41
Wet compressive strength (Mpa)	28
Particle size distribution (mesh size and % weight retained)	0.0 % at 63 μm 15 % at 32 μm
Loose bulk density (kg/m^3)	1100
Compacted bulk density (kg/m^3)	1500

The technical data outlined represents typical figures only. For further details, please contact Saint-Gobain Formula directly.

KEY INFORMATION

Please use with the recommended plaster-water ratio, with a mixing time of approx. 2 to 4 minutes or mix until homogenous. The precise consistency to use will need to be adjusted to suit the individual application. Changes to plaster-water ratio will influence product performance particularly setting time and strength.

PACKAGING AND SHELF LIFE

	Packaging Available	Shelf Life (Month)
Bag	25 kg	9

When stored under dry conditions and in its original packaging, the product will have a specified shelf life that commences from the date of manufacture that is displayed on each sack. Shelf life depends on the packaging type. For those products where a defined 'best before' date is applicable, BBE (Best Before End) followed by the date will be displayed on each sack.

CERTIFICATION

 DoP n° NK001

Tested in accordance with ASTM C59/59M Standard Specification for Gypsum Plaster and Gypsum Molding Plaster

ENVIRONMENT, HEALTH AND SAFETY

Material Safety Data Sheets of Saint-Gobain Formula plasters and gypsum minerals are available for all products and may be obtained directly on our website in the product and documentation sections. No liability is accepted by Saint-Gobain Formula for injury to any person or loss or damage to property by improper use of the product.

DISCLAIMER

This product has been designed for the intended use outlined in this product datasheet. All information herein cancels and replaces any previous document and is provided for sole indicative purpose and is based on Saint-Gobain Formula's knowledge and experience on the date of issuance of this datasheet. Saint-Gobain Formula reserves the right to amend or modify this datasheet. To make sure you are up to date with the latest changes that may have occurred, visit frequently our website. It is advisable to contact Saint-Gobain Formula in case of any doubt arising from the content of such information. Unless otherwise stated, Saint-Gobain Formula's test methods apply. To obtain a copy of the test method, please contact Saint-Gobain Formula directly.

Saint-Gobain Formula shall not be liable for damages or losses of any kind due to an improper use of the product. This datasheet shall not be construed as a substitute for a professional advice before product's use or installation. It is the user's responsibility to use, or install, the products in strict compliance with the applicable norms, standards and professional uses in force on the date of use, or installation.

CONTACT

*For any information, please visit our website
www.saintgobainformula.com*



*Sales
contact*



Documentation



*Technical
information*



*Global
information*